

Conversion of Corn Stover/Wheat Straw Fermentation Residue (FR) to Valuable Resin

Shafqat Abbas*

Department of Chemical Engineering, Minhaj University, Lahore, Pakistan

ABSTRACT

Conversion of stover/wheat straw Fermentation Residue (FR) to valuable resin is a big challenge for current fermentation process. Carbohydrates presents in residue strongly effects on the performance as well as physical properties of the lignin base resin. In this experimental work, we overcome this problem through simple and novel technique for the production of Fermentation residue base resin by the addition of cheapest catalyst sodium hydroxide and Sodium carbonate instead of using poison catalyst lead oxide. FR syntheses from two different residue of fermentation, investigated effects of lignin and carbohydrates on the physical and chemical properties of resin. Synthesized green resin from FR were utilized for the manufacturing of plywood with satisfactory bonding strength (1.09 MPa). Harmful organic compound (formaldehyde) emission reduced to 97%. Synthesis Resin characterized by NMR, DSC, XRD for physical properties, chemical structure and curing behavior of the resin. This work developed a sustainable technology without any waste production.

Keywords: Fermentation residue; Cheapest catalyst; Lignin; Resin

INTRODUCTION

Ethanol is a good and environment friendly bio fuel and developing more rapidly in last four decades. According to World Ethanol and renewable energy sources, ethanol production reached to 28570 million gallons in 2018 [1]. Second generation of Biofuel as an alternative and environment friendly fuel production from waste feedstock such as animal waste, human being waste material, crops waste (baggas, wheat straw, rice straw, corncob, corn straw). Some of them are Lignocellulose waste producing material. These materials required some pretreatments or conditioning for fermentation process for the conversion of waste material to biofuel and wastes residue could be serve as alternative fuel sources or other linin base other valuable compounds. if fermentation process residue can be converted into good quality compound, then ethanol production industry can be adopting cleaner production by the utilization of its all-waste generation resources. During the fermentation process carbohydrates converted in to bioethanol and remaining waste contain mainly lignin, protein, and unconverted cellulosic, hemicellulose material. Some time there was so much unnecessary compound produced during ethanol

production due to feedstock fraction variation, environment condition changing, hidden errors in process parameters but most of them useless is lignin and there is valuable application of it [2]. It is a challenge for pretreatment and separation of lignin from other material then the conversion of lignin to valuable compounds/resin. Resins are complex oil modified polyesters that serves as the film forming agent in some paints and clear coating. Resin and emulsion both are two types of polymer. In recent year study it was investigated that conversion of lignin into resin, aromatic compounds, bio oil, carbon material and polymer matrixed. Huge investment is required for the separation of different types of lignin such as Kraft lignin, organ solve lignin, steam exploded lignin and lignosulfonate so that's why it is cheapest solution to convert into valuable resin instead of separation/reaming in waste and added into pollution fraction. In general fermentation process waste can be directly utilized for the conversion of biogas, animal feed, and bioplastic. Lignin base resin is a valuable and green compound derived from different type resin of waste material. Lignin possess aromatic structure. It is possible to partially substitute lignin for phenol obtained from petroleum industries. Resin is an important material for plywood. according to food and

Correspondence to: Shafqat Abbas, Department of Chemical Engineering, Minhaj University, Lahore, Pakistan, E-mail: engrabbas6@gmail.com

Received date: June 09, 2021; **Accepted date:** June 23, 2021; **Published date:** June 30, 2021

Citation: Abbas S (2021) Conversion of Corn stover/Wheat Straw Fermentation Residue (FR) to Valuable Resin. J Chem Eng Process Technol 12: 24

Copyright: © 2021 Abbas S. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

agricultural organization annually plywood production in 2017 and biggest manufacturer is china producing 204 m. Phenoloms was used as an adhesive but lignin can be convert into resin for this applications. It will decrease the dependency on the phenol base resin. Wheat flour is also using as a raw material for plywood material, 20%-30% (w/w) wheat flour is usually added to the plywood material. Fermentation Residue base resin (FRs) and Lignin base Resins(LRs) that was further characterized the NMR, DSC, XRD. In this study we convert fermentation residue to resin without ant producing waste [3].

MATERIALS AND METHODS

Fermentation residues (R) were obtained from industrial scale plants in Pakistan. R₁ denotes the fermentation residue derived from acid-steam-exploded corn stover supplied by local former. R₂ denotes the fermentation residue that resulted from upto the processing of neutral-steam-exploded wheat stover supplied onim local former). Both R₁ and R₂ were directly used without any of further purification and modification. Phenol (97%), formaldehyde aqueous solution (36%), solid urea (99%), sodium hydroxide (98%), and sodium carbonate (99%) of analytical grade were used without further purification.

Syntheses of fermentation residue-based resin

Resinification was carried out to partially replace phenol with resins in the production of FRs. The synthesis of FRs was carried out in a round bottom flask three necks equipped with temperature sensor as well as heat exchanger/condenser for the condensation of Polycondensation water vapors and equipped with 15 RPM automatic mechanical stirrer. The substitution rate of lignin to phenol was set at 50% (w/w). The lignin content was calculated based on the chemical composition of the fermentation residues. Urea, formaldehyde, and phenol were prepared in the laboratory with a molar pro-portion of 1.0:4.0:1, 5.0:7.0 with two-step reactions. The Resinification was catalyzed by sodium hydroxide and sodium carbonate. In the first step and urea and half of the formaldehyde were placed in the reaction flask, and the temperature was gradually increased to 110°C.

The system was maintained at 110°C for 50 minutes, and it is to pH was maintained at 9.5. During the second step, the remaining formaldehyde, phenol, fermentation residues, sodium hydroxide solution, and carbonate were added to the mixture. The system was maintained at 110°C for 50 minutes, and then it the temperature was reduced to 95°C for 40 minutes. The warm temperature was then decreased to 65°C, and 6.2 g of urea and 30 g of sodium hydroxide solution were added and reacted 40 minutes. The obtained resins were rapidly cooled and stored at room temperature before further uses. LR, FRs separated by centrifuging. The Fermentation residue were characterized by XRD to examine the structural feature [4].

Lignin base resin is a valuable and green compound derived from different type resin of waste material. Lignin possess aromatic structure. It is possible to partially substitute lignin for phenol obtained from petroleum industries. Resin is an important material for plywood. according to food and remaining formaldehyde, phenol, fermentation residues, sodium hydroxide solution, and carbonate were added to the mixture. Resinification was carried out to partially replace phenol with resins in the production of FRs.

RESULTS AND DISCUSSION

Structure and curing behavior characterization of the prepared resins

The solution-state ¹³C NMR and solid-state CP-MAS ¹³C NMR spectra were acquired on a Bruker AV-III 400 MHz spectrometer (Germany). The cured resins were prepared by treating the uncured resins at 135°C for 3 hours in an air convection oven of the DSC analysis of the uncured freeze-dried resins was solutions performed on a Shimadzu DSC-60A (Japan) under a nitrogen atmosphere with a flow rate of 60 mL min⁻¹. Scans were run at is heating rates of 5°C min⁻¹, 10°C min⁻¹, and 15°C min⁻¹. The (R) scanning temperature ranged from 30°C to 200°C.

Properties of the prepared resin adhesives and plywood testing

The viscosity, pH, solid content of the LR and FR adhesives were determined in accordance with the Chinese National Standard (GB/T 14074-2017). The performance of the LR and FRs was tested by preparing plywood and evaluating the formaldehyde emission and bonding strength according to the Chinese National Standard (GB/T 17657-1999). Duplicate three-layer laboratory plywood panels were prepared using LR and FR adhesives and poplar veneers without any curing agent. The FR adhesives were mixed with 20% (w/w, based on the solid resin and water) wheat flour as filler. The LR were firstly adjusted so that the solid content would be the same as that of the FRs. The LR were then mixed with 30% (w/w, based on resin) wheat flour as filler. The glue spread was 325 gm and is the consisted of a single glue line. The plywood was hot-pressed at 125°C under 1.5 MPa for 340s (80 s mm⁻¹). Hot pressing, there for plywood was stored in an ambient environment for 18 hours before further testing. The glue lines in the plywood bonded with FR and LR adhesives were tested Fluorescence Microscopy (FM) according to a previous study.

Chemical composition of fermentation residue

The chemical composition of the fermentation residues was investigated according to the standard laboratory analytical procedure developed by national renewable energy laboratory was (NEREL/TP-51042618) (Table 1).

Composition	R ₁	R ₂
Total Lignin	73.7	60.7
Kalson lignin	65.98	38.9
Acid soluble lignin	2.7	4.8
Carbohydrates	11.06	15.06
Golucose	10.9	13.9
Protein	10.8	12.8
other	4.0	2.0

Table 1: Chemical composition of fermentation residue samples.

Fermentation residue is listed in the Table 1 and comparison of two sample was carried out on the bases of its constituents and lignin is a important element which was converted into resin. In this process polycondensation reaction was occurred between lignin, urea, phenol, formaldehyde As shown in Table 1, both R1 and R2 consisted of a portion of the protein that originated from the enzyme and yeast. Protein is also a feedstock that can be used to produce bio-based resins, which can partially replaced ensure that an equal quantity of adhesives was used to glue each piece of plywood. The bonding strength and formaldehyde and LR was tested for their ability to bond pieces of plywood. Lignin base Resins(LRs) that was further characterized by NMR, DSC, XRD. In this study we convert fermentation residue to which can improve the bonding strength.

Due to the limitations of high viscosity, short durability, and poor water resistance, protein-based resins are unsuitable for wide applications. According to the reported research, alkaline treatment results in the unfolding of the globular structure of protein to allow entry of hydrophilic and hydro-phobic groups to and exposure so that they can make contact with each other, which can improve the bonding strength. In this work, the pH value of the prepared resins was approximately. This ambient alkaline environment properly reduced the viscosity and increased the water tolerance of resins, which was proved by the viscosity and bonding strength, as shown in Table 2. The above results indicated that adding carbohydrates to the lignin-based resin adhesive would significantly improve the performance of wood resin adhesive with this simple and novel process, and this overcame the adverse effect of carbohydrates and protein on the resin adhesive. The excellent performance of the fermentation residue resin adhesive was investigated in detail with properties, structural characterizations, and formation mechanism of FRs in the following sections, especially the synergistic effect of lignin and carbohydrates (Table 2).

Adhesive	Solid content (%)	pH (°C)	(25 Viscosity (22°C, mPa s)	Bonding strength (MPa)	Formaldehyde emission (mg L ⁻¹)
FR1	44.4	12.2	3191.0	1.07	0.17
LR1	38.6	12.1	37.8	0.88	0.11
FR2	41.0	12.0	3503.0	0.78	0.03
LR2	34.3	12.1	16.8	0.60	0.02
GB/T	≥ 35.0	≥ 7.0	≥ 60.0	≥ 0.70 ^a	≤ 0.50

Table 2: Adhesive properties and plywood performance of the FR and LR adhesive.

Properties and performance of prepared resin adhesives

The physical properties of FR and LR adhesives were tested according to the Chinese National Standard (GB/T 14074-2017), and the results are listed in Table 2. The solid content of LR was lower than that of FRs because the SRs separated from

and the results are listed in this listed outs. The solid content of LR was lower than that of FRs because the SRs separated from the FRs. In addition, the viscosity of FRs was higher than that of LR, which implied that the viscosity was also markedly influenced by the SRs. This indicated that the SRs in FRs could perform the same function as that of wheat flour to adjust the viscosity of the adhesive to an optimum condition. The pH values of the FRs and LR were constant, and all reached the Chinese National Standard. The adhesion strength of the FRs and LR was tested for their ability to bond pieces of plywood. The solid content of LR was firstly adjusted so that they contained the same net resins as those in FRs, which would ensure that an equal quantity of adhesives was used to glue each piece of plywood. The bonding strength and formaldehyde emission of plywood were tested according to the Chinese National Standard (GB/T 17657-1999), and the results are shown in Table 2. The bonding strength of the plywood bonded with FRs reached the requirements of exterior-grade panels (first grade, ≥ 0.7 MPa). The bonding strength of the plywood bonded with FR1 and LR1 was distinctly higher than that bonded with FR2 and LR2, and this was due to the carbohydrates in the fermentation residue that hindered the condensation reaction. Formaldehyde pollution of the indoor environment mainly comes from wood panel products. The formaldehyde emission of plywood bonded with FRs met the E0 grade (≤ 0.5 mg/L) as specified by the Chinese National Standard (GB/T 7936.3-48 9846.3-2004), and that with FR2 was extremely low (0.03 mg/L). The low amount of released formaldehyde is beneficial for to this the environment. If wood-based panels are produced using these green FRs, the formaldehyde content will be reduced by a maximum of 94%, as compared with E0 grade. As compared with the traditional Lignin-Phenol-Formaldehyde (LPF) resins adhesives (substitution rate of lignin to phenol was 50% w/w), the bonding strength of FR1 was approximately equal to that of LPF resins. The formaldehyde emission of FR2 was markedly lower than that of LPF resins. It was noteworthy that the process traditional LPF resin adhesives were synthesized with high-purity lignin as the feedstock. Moreover, modification was usually conducted to increase the reactive sites of lignin. In addition, a more optimal comprehensive performance of plywood using FR2 adhesive (solid content 41.0%) was obtained than that of plywood using other ethanol biorefinery residue-based adhesives (solid content 50.0%). 18,36 Both bonding strength met the requirements of the Chinese National Standard, but the formaldehyde emission of the plywood using FR2 adhesive (0.03 mgL⁻¹) was significantly lower than that were the plywood in previous works (0.23 mgL⁻¹).The wood failure one of the plywood bonded with FRs and LR is shown in (Figure 1).

The solid content of LR was firstly adjusted so that they contained the same net resins as those in FRs, which would ensure that an equal quantity of adhesives was used to glue each piece of plywood. The bonding strength and formaldehyde emission of plywood were tested according to the Chinese National Standard (GB/T 17657-1999), and the results are shown in Table 2. The bonding strength of the plywood bonded two sample was carried out on the bases of its constituents and lignin is a important element which was converted into resin. In this process polycondensation reaction was occurred between lignin, urea, phenol, formaldehyde.

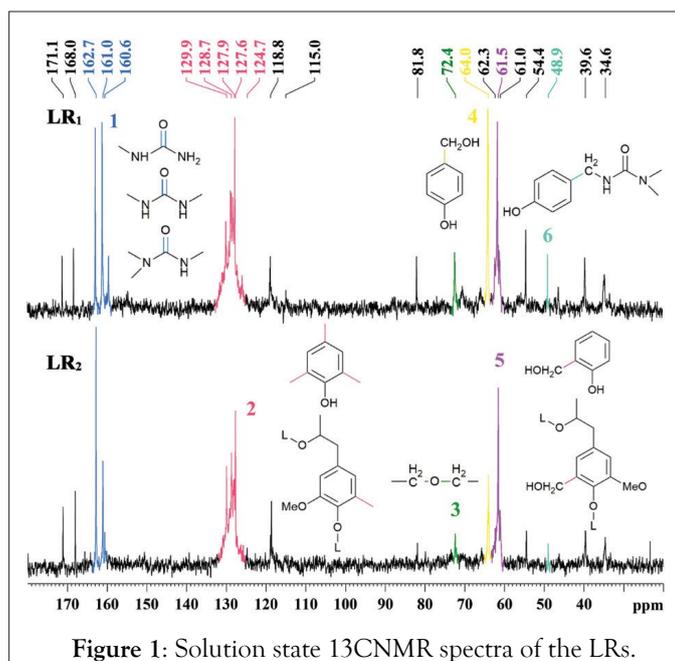


Figure 1: Solution state ^{13}C NMR spectra of the LR1 and LR2.

The wood failure of the plywood bonded with FR1 was markedly higher than that with others, which was consistent with the results of the bonding strength tests. To investigate the functions of each component in the fermentation residue, lignins derived from fermentation residues were also used to produce resins LR3 and LR4, which were compared, and the properties are listed in Table S2. The bonding strength of LR3 and LR4 was lower than that of the FRs. The formaldehyde emission of LR3 and LR4 was extremely higher than that of the FRs and even E0 grade. These results indicated that lignin can react with urea, phenol, and formaldehyde to form lignin-based resin adhesive, while the carbohydrate and protein increased can the viscosity of the resin adhesive to increase the bond strength and suppress the amount of formaldehyde released. Based on the process described above, the fermentation residues from the bioethanol process could be directly used to prepare high quality co-condensed FRs. More importantly, these satisfying results indicated that the addition of carbohydrate could greatly improve the performance of the resin adhesives. Additionally, the direct transformation of the fermentation residues into bulk and high-value products can contribute to the sustainability and cost-effectiveness of both bioethanol production and wood manufacturing [6].

Solution-state ^{13}C NMR of the uncured lignin-based resins

The performance of the resins correlates with their chemical structures. To avoid the disturbance of carbohydrates, the chemical structures of the LR1 and LR2 were investigated by obtaining solution-state ^{13}C NMR spectra. Figure 2 shows the ^{13}C NMR spectra of the freeze-dried uncured LR1 and LR2, while the ^{13}C NMR spectra of the lignin separated from residues are also displayed. The signals were assigned according to previous studies. There were some significant differences between the spectra of LR1 and LR2. The series of peaks from 160.6 to 162.7 ppm were also attributed to the carbonyl peaks of urea, indicating that the urea was mainly substituted. There are signals from the carbonyl groups of mono substituted (162.7 ppm), di substituted (161.0

ppm), and tri substituted (160.6 ppm) urea in LR1. The higher di-substituted and trisubstituted urea of LR1 was markedly higher than that of LR2, which indicated that there were more condensed linkages among urea, phenol, formaldehyde, and lignin. The series of peaks from 124.7 to 129.9 ppm represents the reacted sites of the aromatic nucleus (C-C) in the phenol and lignin (Figure 2).

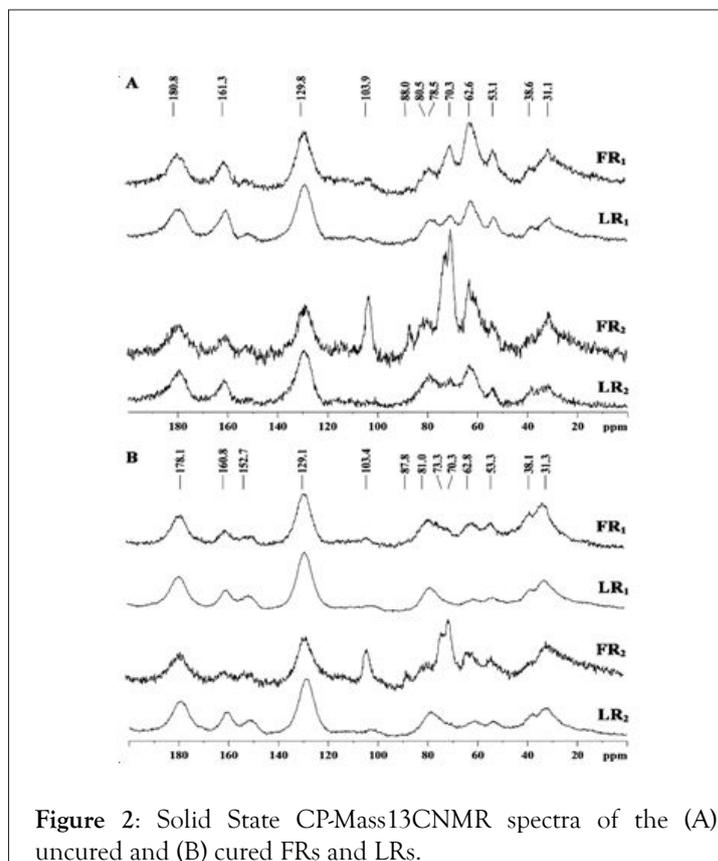


Figure 2: Solid State CP-Mass ^{13}C NMR spectra of the (A) uncured and (B) cured FR1, LR1, FR2, and LR2.

The chemical shift of substituted ortho carbon sites on the aromatic ring in LR1 (127.6 ppm) was obviously stronger than that in LR2. Unsubstituted para and ortho carbons were present at 118.8 ppm and 115.0 ppm, respectively. There were more unsubstituted para carbon sites on the aromatic ring in LR2 as compared to those in LR1. These results indicated that more ortho and para sites in LR1 reacted with formaldehyde and urea than those in LR2. In addition, the unsubstituted ortho carbon sites were scarce both in LR1 and LR2. This was due to the fact that the catalyst Na_2CO_3 hydrolyzed and formed bicarbonate and ions during the synthesis process. The bicarbonate ions accelerated the condensation reaction of formaldehyde or methylol groups towards the ortho positions of benzene rings. The signals around 81.8 ppm belong to methylene glycol ($\text{HO}-\text{CH}_2\text{OH}$, free formaldehyde), especially in LR1. This accounted for the higher formaldehyde emission of the plywood bonded by LR1 than that by LR2. The signals at 72.4 ppm were assigned to the methylene ether linkages formed during the condensation process of phenolic resins. The intensity of the methylene ether peaks of LR1 was markedly stronger than that of LR2. The resin intensity of the peak at 64.0 ppm (*p*-Ph- CH_2OH) and 61.5 ppm (*o*-Ph- CH_2OH) of LR1 was higher than that of LR2. The para position of the phenolic-OH was provided by the phenol, active the para position in phenol was more active as compared to the ortho position. This implied that the carbohydrates in the

fermentation residues formed steric hindrance to impede the condensation reaction of the para position of phenol.

The signals at 54.4 ppm are attributed to the methylene group between urea ($-\text{NH}-\text{CH}_2-\text{N}(\text{CH}_2)-$). The strong signals at phenol 48.9 are assigned to the para co-condensed methylene group ($\text{Ph}-\text{CH}_2-\text{N}(\text{CH}_2)-\text{CO}$). The intensity of the co-condensed peaks lignin of LR1 was obviously higher than those of LR2. In para of addition, this also indicated that the para position of phenol was more active than the ortho position, and the lignin was extremely less active than the phenol [7]. The signals at 39.6 and 34.6 ppm are attributed to p,p $\text{Ph}-\text{CH}_2-\text{Ph}$ and o,p $\text{Ph}-\text{CH}_2-\text{Ph}$, is respectively, and the intensity of these peaks of LRs was nearly the same. According to the results of solution-state ^{13}C NMR, the schematic of the main synthetic route of FRs is shown in the (Figure 3).

Solid-state CP-MAS ^{13}C NMR of the uncured and cured resins

The solid-state CP-MAS ^{13}C NMR technique was chooswd to study the curing behavior of FRs and LRs. The spectra of cured as well as uncured FRs and LRs are shown in Figure 3. The spinning side bands present in the range of 78.5 ppm and 180.8 ppm. The signals of aromatic carbons of methylene ether bridges is 161.3 ppm bridges, some of which was broken during the curing process. The signals around 152.7 ppm and 129.8 ppm are attributed to the phenolic hydroxyl and the substituted aromatic carbons, respectively. The peaks around 103.9, 88.0, 78.5, 70.3, and 62.6 ppm were assigned to carbohydrates, and the intensity of these signals were the strongest for FR2 because of its higher carbohydrate content.

These carbohydrate signals exist in superposition with the signals of co-condensed resins. The peaks around 70.3 ppm decreased as the aliphatic carbons of methylene ether bridges cracked during the curing process. The decrease in the signals around 62.6 was accompanied by an obvious increase at 31.1-23-38.6 ppm. This indicated that the main reaction was that of condensation between methylol groups and remaining unsubstituted para and ortho positions of benzene rings during the curing process. In general, the spectra of the cured FRs were broadly similar in signals.

This signified that the FRs could be directly used to produce phenolic resin adhesives that had stable chemical structures. According to the statistics of the report on China Wood-based Panels Industry 2018, the phenolic resin consumption was reached to 1.43 million tons in the Chinese wood panel industry in 2017. If fermentation residues are used to substitute 50% of the phenol when producing adhesives, the consumption of phenol will be reduced by over 100×10^3 tons/year China, also and the cost of wood manufacture will also decrease [8].

The cellulose crystal structure is a significant property that may result in variation and influence the scarification kinetics during the bioethanol production process. XRD characterized the structure of the fermentation residues (RS) and Solid Residues in (SRs) base resin. The XRD images and the crystallinity index of great importance for the full valorization of lignocellulose, and will decrease chemical dependence on fossil-based resource.

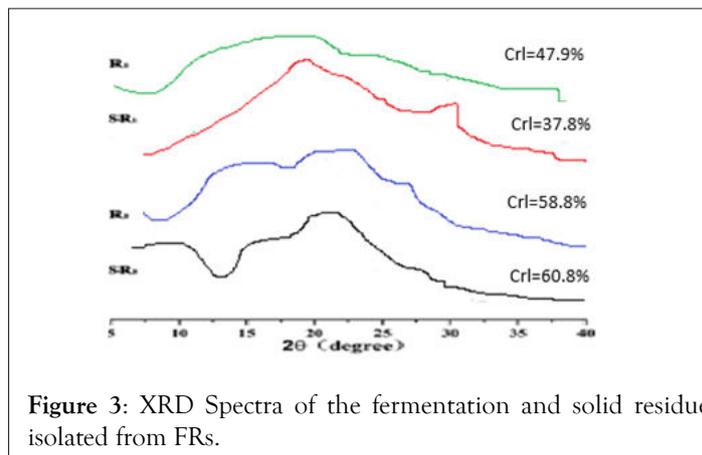


Figure 3: XRD Spectra of the fermentation and solid residue isolated from FRs.

Thermal behavior of the lignin-based resins

The curing process during the manufacturing of resin is a critical and required high attention, and it has a major impact on plywood and play vital role of the performance. The curing kinetic analyses of LRs were performed using Dynamic Scanning Calorimetry (DSC) at different heating rates. The DSC kinetic analysis began by obtaining the kinetic parameters from the first exothermal peak temperatures of the DSC scanning curves at various heating rates. The activation energy data were calculated according to the method of Kissinger (1) and Flynn-Wall-Ozawa Ozawa (2): Fermentation residue can be used for the manufacturing of lignin base high quality resin and having low cost as compared to adhesive/phenolic base resin. Now we present a new technology which produced high quality lignin base resin with producing wastages as well as no need of further purifications. Herein, we developed a simple and novel strategy to successfully overcome this drawback by using bioethanol fermentation residues (lignin-rich substrates) to produce green and high-quality resins without any purification and modification. The eco-friendly FRs can substantially reduce the usage of phenol and the emission of formaldehyde. The co-condensed linkages among urea, formaldehyde, phenol, and lignin were sufficiently abundant so that a firm structure of the resins could be built. The solid residues (carbohydrate-rich substrate) could be satisfactorily used instead of wheat flour to adjust the viscosity, prevent excessive osmosis, and distinctly increase the bonding strength of the resins. Under the synergistic effect of lignin and carbo-hydrates, the fermentations residue-based resins could be utilized to prepare plywood with satisfactory performance. The high-efficiency application of the fermentation residues can realize green production with zero waste, as well as increase the revenue and stimulate the sustainable development of bioethanol manufacturing. This work bridges bioethanol fermentation residues and petroleum-based products, affording a green and sustainable strategy that is of great importance for the full valorization of lignocellulose, and will decrease chemical dependence on fossil-based resources [9].

These carbohydrate signals exist in superposition with the signals of co-condensed resins. The peaks around 70.3 ppm decreased as the aliphatic carbons of methylene ether bridges cracked during the curing process.

X-Ray Diffraction (XRD) analyses of solid residues in fermentation residue-based resins

The cellulose crystal structure is a significant property that may result in variation and influence the scarification kinetics during the bioethanol production process. XRD characterized the structure of the fermentation residues (RS) and Solid Residue of (SRs) base resin. The XRD images and the Crystallinity Index to (CrIs) values of the Rs and SRs were calculated according to the XRD. The peak of amorphous cellulose 17.7° (R1 and SR1) and 18.1° (R2 and SR2), and the peaks at 16.5° and 22.2° are crystalline cellulose. All these types of cellulose exhibited the typical diffraction patterns of cellulose I. The original CrIs of fermentation residues were distinct from the different feedstock and bioethanol processes. The intensity of the signal band around 16.5° of R1 was weaker than that of R2 due to the fact that the feedstock of R1 was pretreated with an acid stream explosion. As we can see, a marked decrease in the CrI was found between R1 and SR1. The main signal around 16.5° and 22.2° was weakened, and no peak appeared at 12.1° . These results confirmed that the cellulose in R1 was in a transition state from cellulose I to cellulose II, and the expansion of the cellulose I lattice occurred under an alkaline environment. In contrast, the CrI of SR2 was nearly the same as that of R2 [10].

The influence of carbohydrate on the performance of resins lignin-based resins are syntheses with high-purity technical lignin. Insufficient attached carbohydrates can reduce the feasibility of lignin usage and impede the condensation reaction due to steric hindrance when synthesizing resins. Furthermore, the carbohydrates would decrease the adhesive power of the cured resins, especially under wet conditions. As shown in Figure 2, the para position of the phenolic-OH was provided and by the phenol, and the para position in phenol was more active than the ortho position. These implied that steric hindrance would result from the carbohydrates in the fermentation residues to impede the condensation. The cellulose could swell under alkaline circumstances, which would result in the amplification of the steric hindrance effect. Moreover, the addition of carbohydrates markedly increased the viscosity of the reaction system and hindered the condensation reaction, which could bring about a heterogeneous reaction and adversely affect the strength of the final resins. However, in this study, the existence of the carbohydrates significantly improved the performance of resins [11-16]. To evaluate the positive effect of carbohydrates, wheat flour was substituted for the SRs and blended with LRs to prepare plywood. The results indicated that the strength of the plywood bonded with FRs was markedly higher than that with LRs, which confirmed that the SRs in the fermentation residues enhanced the bonding strength and were satisfactory substitutes for wheat flour as filler. The satisfactory adhesion strength of FRs also favored water resistance. The glue lines in the plywood using FR and LR adhesives were tested by FM, and the images are shown in Figure 1. The bonding strength and wood failure correlated with the osmosis of the adhesive. There was a markedly greater amount of osmosis of LRs than that of FRs. This result indicated that the SRs in fermentation residues acted as a filler to prevent the excessive osmosis of resin adhesives. The continuous and steady glue line

could favor the bonding strength and wood failure. In general, this is the first time that the effect of solid fermentation residues has been thoroughly investigated. The carbohydrates in fermentation residues may have an adverse effect on the condensation reaction. However, by using SRs as substitutes for wheat flour, not only is the excessive osmosis of adhesives prevented, but also, the decreased use of wheat flour for this purpose will allow more of this resource to be directly used as a food source, thus increasing wheat availability and reserves. Based on these results, the fermentation residues from the bioethanol generation process can be directly used to produce high-performance resins. The synergistic effect of lignin and carbohydrates imparts new possibilities for the utilization of fermentation residues [17-19].

CONCLUSION

Fermentation residue lignin base resin can be used for the manufacturing of plywood with high performance which decrease uses of phenolic resin to produce green resin without further purification required. Hence we investigated new, novel, applicable, easy to control technology for lignin base resin manufacturing. The eco-friendly FRs can substantially reduce the usage of phenol and the emission of formaldehyde. High quality resin is developed by co-condensed linkages among urea, formaldehyde, phenol, and lignin. We can increase viscosity of the resin by using solid fermentation residue instead of wheat flour to prevent more osmosis. The high-efficiency of lignin base resin can realize green production without waste, as well as increase the revenue. This work bridges bioethanol fermentation residues and petroleum-based products, affording a green and sustainable strategy that is of great importance for the full valorization of lignocellulose, and will decrease chemical dependence on fossil-based resources

CONFLICT OF INTEREST

Author have not conflict of interest.

REFERENCES

1. Zhang Y. The links between the price of oil and the value of us dollar. *Int J Energy Econ Policy*. 2013;3:341-351.
2. Wyman CE. Biomass ethanol: Technical progress, opportunities, and commercial challenges. *Annu Rev Energy Environ*. 1999;24:189-226.
3. Lal R. World crop residues production and implications of its use as a biofuel. *Environ Int*. 2005;31:575-584.
4. Zhai R, Hu J, Saddler JN. What are the major components in steam pretreated lignocellulosic biomass that inhibit the efficacy of cellulase enzyme mixtures? *ACS Sustain Chem Eng*. 2016;4:3429-3436.
5. Satari B, Karimi K, Kumar R. Cellulose solvent-based pretreatment for enhanced second-generation biofuel production: A review. *Sustain Energy Fuels*. 2019;3:11-62.
6. Balat M. Production of bioethanol from lignocellulosic materials the biochemical pathway: A review. *Energy Convers Manag*. 2011; 52:858-875.
7. Lynd LR, Liang X, Bidy MJ. Cellulosic ethanol: Status in innovation *Curr Opin Biotechnol*. 2017;45:202-211.

8. Balan V, Chiaramonti D, Kumar S. Review of US and EU initiatives toward development, demonstration, and commercialization of lignocellulosic biofuels. *Biofuels Bioprod Biorefin.* 2013;7:732-759.
9. Lane J. Enviral licenses Clariant's sunliquid technology for commercial-scale cellulosic ethanol project in Slovakia. 2017.
10. Kennedy HT. Breaking the Bottleneck—POET-DSM achieves cellulosic biofuel breakthrough. 2017.
11. Bing Ma P, Zhao C, Rakesh AS. A synergistic biorefinery based on catalytic conversion of lignin prior to cellulose starting from the lignocellulosic biomass. *Green Chem.* 2015;17:1321-928.
12. Chovau S, Degrauwe D, Van B. Critical analysis of techno-economic estimates for the production cost of lignocellulosic bioethanol. *Renew Sustain Energy Rev.* 2013;26:307-21.
13. Huang HJ, Ramaswamy S, Al-Dajani W. Effect of biomass of to species and plant size on cellulosic ethanol: A comparative process and economic analysis. *Biomass Bioenerg.* 2009;33:234-246.
14. Humbird D, Davis R, Tao L. Process design and economics for biochemical conversion of the lignocellulosic biomass to ethanol. Colorado: National Renewable Energy Laboratory. 2011.
15. Kumar R, Tabatabaei M, Karimi K. Recent updates on lignocellulosic biomass derid e thanol: A r evie w. *Biofuel Res J.* 2016;9:347-356.
16. Laxman RS, Lachke AH. Bioethanol lignocellulosic biomass. In: *Handbook plant-based biofuels*; 2009;121-139.
17. Hamad WY, Hu TQ. Structure-process-yield interrelations in nanocrystalline cellulose extraction. *Can J Chem Eng.* 2010;88:392-402.
18. Saha BC. Hemicellulose bioconversion. *J Ind Microbiol Biotechnol.* 2003;30:279-291.
19. Lin SY, Lebo SE. Lignin. In: John Wiley and Sons I, editor. *Kirk-Othmer. Encycl Chem Technol.* 2001;1-32.