

Suitability of Amorphous Thin – Film Alloys for Hydrogen Purification

Shahrouz Nayebossadri*, John D. Speight and David Book

School of Metallurgy and Materials, University of Birmingham, Edgbaston, Birmingham, B15 2TT, UK

*Corresponding author: Shahrouz Nayebossadri, School of Metallurgy and Materials, University of Birmingham, Edgbaston, Birmingham, B15 2TT, UK, Tel: (+44) (0) 121 414 5213; E-mail: s.nayebossadri@bham.ac.uk

Received date: November 28, 2017; Accepted date: November 28, 2017; Published date: December 27, 2017

Copyright: © 2018 Nayebossadri S, et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

Introduction

Hydrogen separation membranes combined with Steam Methane Reforming (SMR) or Coal Gasification (CG) could provide a high volume of ultra-high purity hydrogen provided that the cost of separation membranes is reduced in line with US DoE targets [1]. Dense metallic membranes used for hydrogen purification are dominantly based on Pd and Pd alloys [2,3]. However, the application of Pd and Pd alloy membranes for large-scale hydrogen purification is too expensive [1]. In addition to the high cost of Pd, the susceptibility to hydrogen embrittlement [4] and surface poisoning by impurity gases such as CO₂, CO and H₂S [5], encourage searching for alternative hydrogen separation materials.

Amorphous alloys have been investigated as potential hydrogen purification membranes because of their good mechanical properties, corrosion resistance, higher resistance to hydrogen embrittlement, and significantly lower cost [6]. Some of the amorphous zirconium and nickel-based alloys have been shown by computational [7,8] and experimental studies [7,9] to have hydrogen permeability values close to that of Pd. For example, (Ni_{0.6}Nb_{0.4})₇₀Zr₃₀ alloy showed comparable hydrogen permeability to Pd (1.3×10^{-8} mol m⁻¹ s⁻¹ Pa^{-0.5} at 400°C) while offering acceptable surface catalytic activity for hydrogen dissociation/recombination. The hydrogen permeability in this alloy showed to increase by increasing the Zr content, but forming a less thermally stable alloy [9,10]. Zr₅₄Cu₄₆ and Zr₃₀Cu₆₀X₁₀ (X=Sc, Ta, Y,

and Ti) alloys were also computationally predicted to offer higher hydrogen permeability than Pd [11,12]. However, the surface oxidation could significantly lower the hydrogen permeability in these alloys [13].

In general, higher hydrogen solubility is seen in amorphous alloys due to an increased in the population of defective sites suitable for hydrogen occupation [14]. Unlike the crystalline materials, hydrogen diffusivity in amorphous materials depends on the hydrogen concentration. This attributes to the existence of hydrogen occupation sites with different binding energies. Initially, hydrogen mobility is low due to the occupation of high-energy sites with higher hydrogen affinity. As hydrogen concentration increases and high-energy sites are filled, hydrogen atoms will occupy low-energy sites, which results in a higher mobility as hydrogen is not strongly bound to these sites [15].

Fabrication of thinner membrane can significantly improve the hydrogen diffusion in membranes and therefore achieving a higher permeability. Amorphous membranes with thicknesses of 30 to 50 μm [16] were successfully fabricated by melt spinning. We also recently demonstrated [17] the possibility to fabricate dense binary and ternary Zr-based amorphous thin-films (less than 10 micron) by the Closed Field Unbalanced Magnetron Sputtering Ion Plating (CFUMSIP) (Figure 1). Using this method, we could produce amorphous thin-films in a wider compositional range with a better control over the size, shape and thickness of the films.

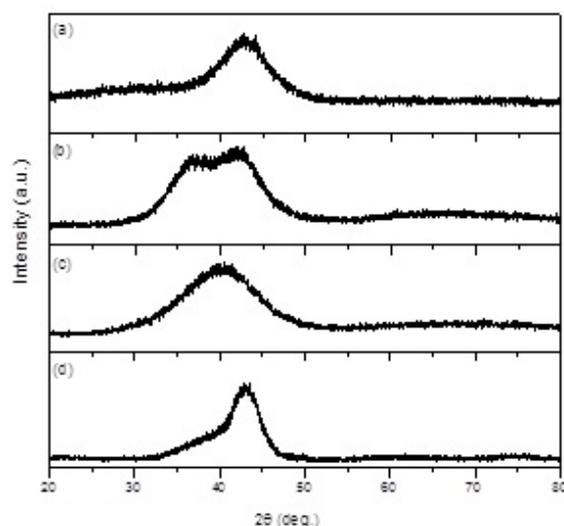


Figure 1: XRD patterns of (a) Zr_{40.5}Ni_{59.5}, (b) Zr_{56.2}Cu_{43.8}, (c) Zr₃₀Cu_{57.7}Y_{12.3}, and (d) Zr₃₂Cu_{57.3}Ti_{10.7} thin-films fabricated by CFUMSIP system (right picture).

The metastable thermodynamic state of amorphous membranes imposes temperature limitation during the amorphous membranes operation. Crystallisation can occur in amorphous membranes at high temperatures during the operation and even below the theoretical crystallisation temperature if kept for a long time [18]. Upon crystallisation, alloys will lose their resistance to hydrogen embrittlement followed by a substantial decrease in the alloy's hydrogen permeability. We noticed [19] that thermal stability of the fabricated thin-films is mainly dominated by the alloys composition rather than the fabrication route. However, the crystallisation process in these films seemed to be different compared to bulk materials. Alloys were particularly sensitive to the oxidation and amorphous phase decomposition during structural analysis under inert and hydrogen atmospheres. As a result, phase separation was substantial in the case of Cu and Ni in the $Zr_{56.2}Cu_{43.8}$ and $Zr_{40.5}Ni_{59.5}$ sputtered thin-film alloys. Cu and Ni phase separation could effectively alter the local atomic structure, hence affecting the crystallisation thermodynamic. An effective method to reduce the level of Cu phase separation was [19] to fabricate $Zr_{30}Cu_{57.7}Y_{12.3}$, and $Zr_{32}Cu_{57.3}Ti_{10.7}$ ternary amorphous thin-films. However, the kinetic studies revealed that the atomic size mismatch of Y and Ti in these ternary alloys may change the local atomic microstructure and reduce the atomic packing density. Thermal behaviour of amorphous alloys strongly depends on the existence of the Short Range Order (SRO) metastable icosahedra-like clusters with highest atomic packing density. The formation of crystal like structure was encouraged in the $Zr_{30}Cu_{57.7}Y_{12.3}$, and $Zr_{32}Cu_{57.3}Ti_{10.7}$ ternary amorphous thin-films, which could act as nucleation sites and therefore reducing the thermal stability of the alloys.

Although, some amorphous binary and ternary Zr-based alloys proposed to offer a comparable hydrogen permeability to Pd, oxidation, phase separation and the lack of thermal stability, especially under hydrogen, can hinder the application of amorphous thin-film membranes. The suitability of amorphous thin-films (and even bulk alloys) as potential hydrogen purification membranes can be better judged after more careful studies on the crystallisation mechanism and thermal stability controlling factors under hydrogen.

References

1. Criscuoli A, Basile A, Drioli E, Loiacono O (2001) An economic feasibility study for water gas shift membrane reactor. J Membr Sci 181: 21–27.
2. Uemiya S (2004) Brief review of steam reforming using a metal membrane reactor. Top Catal 29: 79–84.
3. Rahimpour MR, Samimi F, Babapoor A, Tohidian T, Mohebi S (2017) Palladium membranes applications in reaction systems for hydrogen separation and purification: A review. Chem Eng Process Process Intensif 121: 24–49.
4. Jayaraman V, Lin YSS (1995) Synthesis and hydrogen permeation properties of ultrathin palladium-silver alloy membranes. J Membr Sci 104: 251–262.
5. Chen CH, Ma YH (2010) The effect of H₂S on the performance of Pd and Pd/Au composite membrane. J Membr Sci 362: 535–544.
6. Dolan MD (2010) Non-Pd BCC alloy membranes for industrial hydrogen separation. J Membr Sci 362: 12–28.
7. Dolan M, Dave N, Morpeth L, Donelson R, Liang D, et al. (2009) Ni-based amorphous alloy membranes for hydrogen separation at 400°C. J Membr Sci 326: 549–555.
8. Hara S, Sakaki K, Itoh N, Kimura HM, Asami K, et al. (2000) An amorphous alloy membrane without noble metals for gaseous hydrogen separation. J Membr Sci 164: 289–294.
9. Kim SM, Chandra D, Pal NK, Dolan MD, Chien WM, et al. (2012) Hydrogen permeability and crystallization kinetics in amorphous Ni-Nb-Zr alloys. Int J Hydrogen Energy 37: 3904–3913.
10. Paglieri SN, Pal NK, Dolan MD, Kim SM, Chien WM, et al. (2011) Hydrogen permeability, thermal stability and hydrogen embrittlement of Ni-Nb-Zr and Ni-Nb-Ta-Zr amorphous alloy membranes. J Membr Sci 378: 42–50.
11. Hao S, Sholl DS (2011) Computational prediction of durable amorphous metal membranes for H₂ purification. J Membr Sci 381: 192–196.
12. Hao S, Sholl DS (2013) Rapid prediction of hydrogen permeation through amorphous metal membranes: an efficient computational screening approach. Energy Environ Sci 6: 232.
13. Lai T, Yin H, Laura Lind M (2015) The hydrogen permeability of Cu-Zr binary amorphous metallic membranes and the importance of thermal stability. J Membr Sci. 489, 264–269.
14. Wipf H (1998) Solubility and Diffusion of Hydrogen in Solid Metals. Met Forum 1979, 2, 138–148.
15. dos Santos DS, de Miranda PEV. Hydrogen solubility in amorphous and crystalline materials. Int J Hydrogen Energy 23: 1011–1017.
16. Dolan MD, Dave NC, Ilyushechkin AY, Morpeth LD, McLennan KG (2006) Composition and operation of hydrogen-selective amorphous alloy membranes. J Membr Sci 285: 30–55.
17. Nayebossadri S, Smith D, Speight J, Book D (2015) Amorphous Zr-based thin films fabricated by magnetron sputtering for potential application in hydrogen purification. J Alloys Compd 645: S56–S60.
18. Ockwig NW, Nenoff TM (2007) Membranes for hydrogen separation. Chem Rev 107: 4078–4110.
19. Nayebossadri S, Greenwood CJ, Speight JD, Book D (2017) Thermal and structural stability of Zr - based amorphous thin films for potential application in hydrogen purification. Sep Purif Technol 187: 173–183.