

# The Impact of the Physiochemical Properties of Manufactured Nanoparticles on *In vitro* and *In vivo* Evaluation of Particle Toxicity

Masanori Horie<sup>1\*</sup> and Hitoshi Iwahashi<sup>2</sup>

<sup>1</sup>Health Research Institute, National Institute of Advanced Industrial Science and Technology (AIST), Takamatsu, Kagawa, Japan

<sup>2</sup>Faculty of Applied Biological Sciences, Gifu University, Gifu, Japan

## Abstract

Recently, many *in vitro* studies evaluating the effects of nanoparticles on cellular physiology have been reported. In *in vitro* systems, the nano-objects induce not only primary effects but also confounding (artificial) effects. Investigations into the physiological and pathological effects induced in cells by *in vitro* exposure to nano-objects may be confounded by the specific physical and chemical properties of the objects. For example, protein adsorption from the culture media to the surfaces of nano-objects can essentially starve the cells. In addition, certain nanoparticles can release metal ions into cell culture or bioassay reagents. The protein adsorption and metal ion release by the nano-objects can interfere with ELISA and LDH assays, producing inaccurate results. Moreover, unstable or non-homogenous suspensions of nano-objects can result in imprecise *in vitro* evaluations of nano-objects. For accurate *in vitro* testing of nanoparticles, we should consider the effects of these three important properties of nanosuspensions: protein adsorption, metal ion release, and suspension stability.

**Keywords:** Nano-object; Nanosuspension; Adsorption; Metal ion; Suspension stability

## Introduction

A nano-object is defined as an object with one or more external dimensions being nanoscale (1-100 nm). A nano-object includes three kinds of materials, a nanoplate, a nanofiber, and a nanoparticle (Figure.1). Nano-objects, particularly metal oxides, metal nanoparticles, and nanocarbons, have various industrial and medical applications. As the field of nanotechnology shifts from scientific study to engineering, the application focus shifts from the laboratory to the market. In the past ten years, various studies describing the biological effects of nano-objects have been reported. Evaluations of the biological activity of manufactured nanoparticles have been performed both in cell culture (*in vitro*) and in animal models (*in vivo*). *In vitro* testing is used to understand the toxic mechanisms of nanoparticles and as pre-screening for the *in vivo* tests. Thus, *in vitro* testing plays an important role in the evaluation and understanding of nanotoxicity. Although the *in vivo* tests are essential for determining the total toxic effect of the particles, such as establishing a no observable adverse effect level (NOAEL) for exposure, the *in vivo* system is complex. In order to understand the biological mechanisms of nanoparticle activity, simplified *in vitro* systems are simple essential. In addition, compared with *in vitro* systems, *in vivo* modeling is expensive and time-consuming. Thus, pre-screening of test materials by *in vitro* testing is beneficial. With regard to nanoparticle-induced inflammation and oxidative stress, the *in vitro* data correspond to the results of the *in vivo* tests [1,2]. However, some evaluations, such as that of the carcinogenicity of nanoparticles, are problematic *in vitro*.

As describes above, *in vitro* testing is essential to evaluate the biological activity of nanoparticles, however, it has been recently suggested that the physical and chemical features of nanoparticles can affect the results of *in vitro* experiments [3,4]. For example, results of *in vitro* tests are sometimes influenced by the physical properties of the nanoparticle suspension [5-8]. Therefore, characterization of the suspension is important for accurate interpretation of data produced by *in vitro* testing. Without properly characterization of the test suspension, the results of nanotoxicity test may be misinterpreted. In some cases, we can observe “confounding” effects caused by the specific

physical and chemical properties of the nanoparticle. The confounding effect is an artificial effect in many cases. These confounding effects are specific to *in vitro* experimentation, because they either do not occur or have minimal effect *in vivo*. Importantly, nanoparticle-induced effects observed *in vitro* must be confirmed *in vivo*. If the effect is observed only *in vitro*, it is possibly not toxicologically relevant. Therefore, investigators should distinguish between the primary effects and confounding effects of nanoparticles when evaluating biological

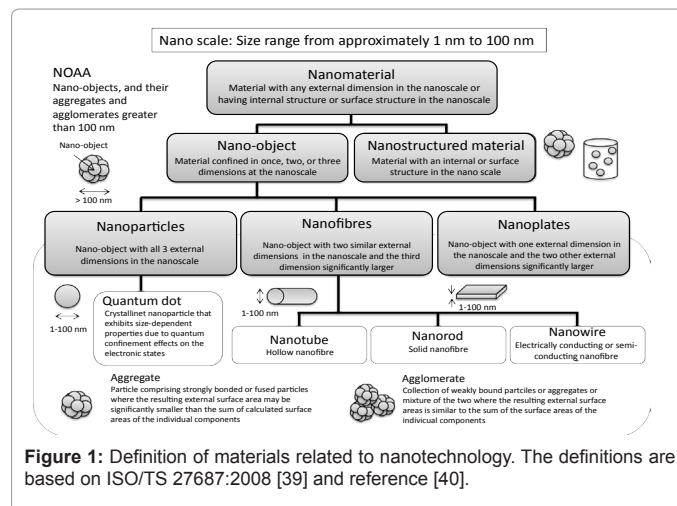


Figure 1: Definition of materials related to nanotechnology. The definitions are based on ISO/TS 27687:2008 [39] and reference [40].

\*Corresponding author: Masanori Horie, Health Research Institute, National Institute of Advanced Industrial Science and Technology (AIST), 2217-14 Hayashi-cho, Takamatsu, Kagawa 761-0395 Japan, Tel: +81-87-869-4197; E-mail: [masa-horie@aist.go.jp](mailto:masa-horie@aist.go.jp)

Received March 01, 2014; Accepted April 26, 2014; Published April 28, 2014

Citation: Horie M, Iwahashi H (2014) The Impact of the Physiochemical Properties of Manufactured Nanoparticles on *In vitro* and *In vivo* Evaluation of Particle Toxicity. J Phys Chem Biophys 4: 139. doi:10.4172/2161-0398.1000139

Copyright: © 2014 Horie M, et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

outcomes. Table 1 summarizes the primary and confounding effects of nanoparticles on *in vitro* and *in vivo* tests and the biological relevance. In this review, we examine the necessary factors for accurate *in vitro* testing of nanoparticles. We focus on three important properties of nanoparticles: (1) adsorptive properties, (2) release of metal ions, and (3) stability of the suspension.

### Adsorption Properties of Nanoparticles

Most important confounding influence nanoparticles may have on an *in vitro* system is surface adsorption. Compared with micro-scale particles, nanoparticles have large surface areas and thus, nanoparticles adsorb proteins and salts from the culture medium [9]. In many cases, fetal bovine serum (FBS) and/or horse serum is added to the medium as a supply of essential nutrients and growth factors. When nanoparticles are added to a serum-supplemented medium, serum proteins immediately adsorb to the nanoparticles and form a protein layer on the surface, which called a “protein corona.” [10]. The protein corona is involved in the adhesion of the nanoparticles to the cellular surface [11,12]. A major protein present in serum is serum albumin. Bovine serum albumin (BSA) shows negative zeta potential at neutral pH [13,14]. Nanoparticles with a positive zeta potential adsorb more BSA than do nanoparticles with a negative zeta potential. The zeta potential of nanoparticle in the culture medium is dependent upon the adsorbed proteins. Since the nanoparticles adsorb BSA present in culture medium rather than water, the zeta potential of the nanoparticles is negative. In many cases, it is approximately -10 to -30 mV [15-17] (Table 2). Zeta potential influences the cellular uptake of nanoparticles indirectly via protein adsorption [18], and whether or not particles adsorb large amounts of protein is an important *in vitro* property of the nanoparticles. However, nanoparticles can also adsorb proteins *in vivo*. Biological fluids such as saliva, pulmonary surfactant, and skin moisture are largely made up of proteins and inhaled or administered nanoparticles may adsorb these proteins. Therefore, protein adsorption and formation of the protein corona occurs not only *in vitro* but also *in vivo*, and thus contribute to the biological effects of nanoparticle. On the other hand, protein adsorption by nanoparticles can also cause confounding effects *in vitro*.

Adsorption of medium components onto the nanoparticles leads

Influential factor	Effect for experimental systems	<i>in vitro</i> test	<i>in vivo</i> test	
Adsorption ability	Adsorption of molecules to particles	Yes	Yes	primary effect
	Influence of adsorption effect on experimental result. (Starvation effect, adsorption of marker molecules, etc.)	Yes	No	confounding effects (artificial)
Metal ion release	Metal ion release from nanoparticles	Yes	Yes	primary effect
	Accumulation of metal ions in experimental system	Yes	No	confounding effects (artificial)
	Influence to experimental reaction such as ELISA	Yes	No	confounding effects (artificial)
Stability of nanosuspension	Formation of secondary particles, aggregates and/or agglomerates	Yes	Yes	primary effect
	Accumulation of the large secondary particles onto cells by gravitational settling	Yes	No	confounding effects (artificial)

**Table 1:** Important factors of nanotoxicology and these effects on experimental systems.

Nanoparticle	Primary particle size (nm)	Zeta potential (mV)		Reference
		Water	DMEM, 10% FBS	
TiO <sub>2</sub>	11	-8	-10	[25]
ZnO	13	-15	-5	[25]
CeO <sub>2</sub>	8	+15	-10	[25]
Nanodiamond	Unknown	-51.66	-23.7	[41]
Nanodiamond	Unknown	+42.39	-11.29	[41]
Nanodiamond	Unknown	+45.58	-11.93	[41]

**Table 2:** Zeta potential of nanoparticles in water and culture medium.

to the depletion of media nutrients and starvation of the cells. In addition, nanoparticles adsorb salts such as calcium from the medium [8,9]. Calcium starvation causes changes in cellular morphology change and growth inhibition [3]. The lipids present in serum may also be adsorbed by the nanoparticles; however, the influence of lipid adsorption on cellular physiology is still unclear. The cellular starvation associated with nanoparticle exposure is an artificial effect specific to the closed experimental *in vitro* systems. Nanoparticle-induced cellular starvation does not occur *in vivo*, because nutrients are continually replenished. Therefore, the biological effects of nanoparticles can be overestimated using cell culture systems in which do not account for this starvation affect. In addition, nanoparticles can adsorb secreted cellular proteins such as cytokines and lactate dehydrogenase (LDH). The levels of these secreted proteins are frequently used as markers of inflammation and cytotoxicity. Nanoparticle exposure can induce the secretion of inflammatory cytokines by cells or physically injure cellular membranes, resulting in LDH release into the surrounding medium. Thus, experimental methods that rely upon cytokine or LDH release as measurements of nanoparticle-induced toxicity may significantly underestimate particle effects [3,6]. Therefore, *in vitro* evaluation of nanoparticles should carefully account for these confounding effects.

### Metal ion Release

In some cases, nanoparticles are more soluble than micro-scale particles. It has been reported that ZnO, CuO NiO, Cr<sub>2</sub>O<sub>3</sub>, and MgO nanoparticles can release their metal ions into the culture medium [15,19]. Silver nanoparticles also show cytotoxicity by Ag<sup>+</sup> release [20]. Many of these metal ions, such as Zn<sup>2+</sup>, Cu<sup>2+</sup>, Ni<sup>2+</sup> and Ag<sup>+</sup>, have cytotoxic activity. The “soluble” nanoparticles show not only extracellular metal ion release but also intracellular metal ion release after cellular uptake [21]. Extracellular metal ions have the same cytotoxicity mechanisms as soluble metal compounds such as ZnCl<sub>2</sub>. The uptake of extracellular metals is regulated by specific membrane ion channels, and therefore, metal ions do not easily traverse cellular membranes [22]. For example, extracellular Ni<sup>2+</sup> influx into cells is blocked by calcium channels [23]. On the other hand, phagocytosis of nanoparticles results in the release of the metal ions inside the cell. Consequently, intracellular metal ion concentrations increase, and various cytotoxic mechanisms are induced, such as enhanced oxidative stress and enzyme dysfunction [2,24]. Thus, nanoparticles behave as both particles and metals in the cell.

Additionally, dissolution rate of nanoparticles is also important. The dissolution rate is different in the kind of the dispersant. In many cases, nanoparticles more soluble in the medium than the water. For instance, ZnO nanoparticles showed different solubility by the medium and water [25]. There is a report that the solubility of silver nanoparticles depended on the concentration of Cl<sup>-</sup> [26]. Solubility of nanoparticles in the biological fluids such as saliva, the pulmonary surfactants, and

the sweats might be also different. And surface property of the nano-object affect to a biodurability [27]. The dissolve rate is important for not only the cytotoxicity but also biodurability.

The cytotoxic activity of nanoparticles depends upon which metal is released. Previous studies report that ZnO and CuO nanoparticles release  $Zn^{2+}$  and  $Cu^{2+}$ , respectively, into the culture medium, where they induce severe cellular oxidative stress [2,15,28,29]. On the other hand, although MgO and  $CaCO_3$  nanoparticles also release  $Mg^{2+}$  and  $Ca^{2+}$ , the ions are relatively benign [15,30]. In addition, “insoluble” nanoparticles such as  $TiO_2$  and  $CeO_2$  produce only minor biological effects compared to those of “soluble” nanoparticles [15]. The activities of metal ions released from nanoparticles are also observed *in vivo*. In particular, the pulmonary toxicity of “soluble” nanoparticles such as ZnO and NiO is more severe than that of “insoluble” nanoparticles such as  $TiO_2$  [31].

Metals released from nanoparticles are responsible for not only the primary physiological effects but also confounding effects on *in vitro* systems. For example, some metal ions affect LDH activity. The LDH assay is one of the most widely used methods for ascertaining cytotoxicity. Damage to the cellular membrane induced by toxic agents such as nanoparticles results in leakage of the intracellular enzyme LDH into the surrounding medium. In many LDH assay kits, leaked LDH is determined based on its enzymatic activity. However, certain metals such as  $Zn^{2+}$  and  $Cu^{2+}$  can inhibit LDH activity, and thus, cellular viability is overestimated. In addition, high concentrations of  $Zn^{2+}$  can interfere with ELISA reactions [32]. The release of metals from nanoparticles *in vivo* into body fluids such as saliva, pulmonary surfactant, and blood may decrease over time. However, a measurement of the released metal concentration *in vivo* is difficult to obtain, and very little is known about the kinetics of metal release *in vivo*. In contrast, an *in vitro* system is closed system. The released metals accumulate and the metal concentration in the system increases with time. Therefore, the metal ion concentration differs between *in vivo* and *in vitro* systems. As such, an understanding of the metal ion concentration in the nano-object suspension is important for the evaluation of biological activity.

### Stability of the Nanosuspension

Nanoparticles form aggregates and/or agglomerates in suspension. In particular, they form larger aggregates/agglomerates in suspension fluids with a high salt concentration such as cell culture medium. The nanoparticle aggregates, in turn, can form secondary particles consisting of a complex between the aggregate and adsorbed proteins [3]. In the unstable suspension, a gravitational settling of the large secondary particles occurs. In cell culture testing, precipitation of the particles results in a non-homogenous exposure and alterations in the effective concentration of particles that the cells receive. Furthermore, while secondary particles in a stable suspension enter cells via diffusion, in an unstable suspension, the secondary particles reach the cells by diffusion and/or gravitational settling [33,34].

Particle size can also influence the biological effects of nanoparticles. Nanoparticle suspensions include secondary particles of various sizes and the size of the secondary particle that reaches any given cell might be different depending on the exposure time. For example, secondary particles of  $TiO_2$  nanoparticles in the range of 90-130 nm had minimal effects on cell viability and induction of oxidative stress [35]. Thus, although the effects of secondary particle size on cellular physiology is still unclear, this association of secondary particle size with a biological effect is a primary effect of stable suspensions of nanoparticles. On the other hand, if large secondary particles accumulate on cells by

gravitational settling, the effective cellular exposure concentration of the nanoparticles is difficult to determine and will not reflect the suspension concentration. Furthermore, large amounts of accumulated particles on cellular surfaces may alter the biological effects of the particles, which will differ from the effects produced by stable suspension. Therefore, an understanding of the stability of the nano-object suspension is important for the evaluation of biological activity (reviewed in reference [4]).

### Other Factors of Note

Other physicochemical properties of nanoparticles should be taken into consideration when evaluating biological effects *in vitro* vs. *in vivo*. The pH of the nano-object suspension is important for cellular metabolism and growth. Although commonly used culture medium such as MEM, DMEM and RPMI 1640 have pH buffering ability, the release of large amounts of metal ions from nanoparticles can lead to pH changes in the medium. These pH changes alter cellular physiology to a greater extent in the closed *in vitro* system than *in vivo*. On the other hand, the pH of the medium also changes with cellular metabolism, and the culture medium becomes more acidic over time. Although the biological consequences of pH changes are minimal, understanding how pH affects nanoparticle-induced toxicity is important.

The potential endotoxin contamination of nanoparticle preparations should be also noted. Contamination of endotoxin affects the expression of inflammatory markers such as IL-1 and IL-8. Adsorbed endotoxin on the surface of nanoparticles confounds experimental results. Moreover, nanoparticles interfere with the limulus amoebocyte lysate (LAL) test used to detect endotoxin [7,36]. These observations should be taken into consideration when analyzing nanoparticle-induced cytokine expression *in vitro*.

Finally, the concept of “cell vision” needs to be considered [37]. The cellular responses induced by nanoparticles such as induction of oxidative stress, apoptosis and cell membrane injury are similar regardless of the cell type. However, the strength and specificity of these responses differ by cell type. For example, macrophages produce proinflammatory cytokines such as IL-1 $\beta$  and TNF- $\alpha$ . The cytotoxic effect of these cytokines on nerve cells is more pronounced than for epithelial cells [38]. Thus, the most suitable cell type should be selected for experimentation.

### Conclusion

The purpose of *in vitro* testing in toxicology is different from that of *in vivo* examinations. The *in vitro* test is not simply an alternative evaluation tool to an *in vivo* examination. One of the important purposes of *in vitro* testing is to understand the mechanisms of the biological activities of nanoparticles. We can obtain holistic information on the biological consequences of nanoparticle exposure from *in vivo* tests. For example, evaluation of carcinogenicity of a nanoparticle only by *in vitro* testing is insufficient. For the effective evaluation of the biological responses to nanoparticles, it is important to understand the advantages and the limitations of *in vivo* and *in vitro* tests. Sometimes, the nanoparticles induce confounding effects *in vitro*. For accurate evaluation of cellular responses to nanoparticles, an understanding of the properties of nanoparticles-medium suspensions is important. At a minimum, the measurement of three properties is necessary: (1) protein adsorption, (2) metal ion release, and (3) suspension stability.

## References

1. Horie M, Fukui H, Nishio K, Endoh S, Kato H, et al. (2011) Evaluation of acute oxidative stress induced by NiO nanoparticles *in vivo* and *in vitro*. J Occup Health 53: 64-74.
2. Fukui H, Horie M, Endoh S, Kato H, Fujita K, et al. (2012) Association of zinc ion release and oxidative stress induced by intratracheal instillation of ZnO nanoparticles to rat lung. Chem Biol Interact 198: 29-37.
3. Horie M, Kato H, Iwahashi H (2013) Cellular effects of manufactured nanoparticles: effect of adsorption ability of nanoparticles. Arch Toxicol 87: 771-781.
4. Horie M, Kato H, Fujita K, Endoh S, Iwahashi H (2012) *In vitro* evaluation of cellular response induced by manufactured nanoparticles. Chem Res Toxicol 25: 605-619.
5. Wale-Knirsch JM, Pulskamp K, Krug HF (2006) Oops they did it again! Carbon nanotubes hoax scientists in viability assays. Nano Lett 6: 1261-1268.
6. Zaqout MS, Sumizawa T, Igisu H, Wilson D, Myojo T, et al. (2012) Binding of titanium dioxide nanoparticles to lactate dehydrogenase. Environ Health Prev Med 17: 341-345.
7. Dobrovolskaia MA, Neun BW, Clogston JD, Grossman JH, McNeil SE (2013) Choice of method for endotoxin detection depends on nanoformulation. Nanomedicine (Lond).
8. Casey A, Herzog E, Lyng FM, Byrne HJ, Chambers G, et al. (2008) Single walled carbon nanotubes induce indirect cytotoxicity by medium depletion in A549 lung cells. Toxicol Lett 179: 78-84.
9. Horie M, Nishio K, Fujita K, Endoh S, Miyauchi A, et al. (2009) Protein adsorption of ultrafine metal oxide and its influence on cytotoxicity toward cultured cells. Chem Res Toxicol 22: 543-553.
10. Cedervall T, Lynch I, Lindman S, Berggard T, Thulin E, et al. (2007) Understanding the nanoparticle-protein corona using methods to quantify exchange rates and affinities of proteins for nanoparticles. Proc Natl Acad Sci U S A 104: 2050-2055.
11. Lesniak A, Fenaroli F, Monopoli MP, Åberg C, Dawson KA, et al. (2012) Effects of the presence or absence of a protein corona on silica nanoparticle uptake and impact on cells. ACS Nano 6: 5845-5857.
12. Lesniak A, Salvati A, Santos-Martinez MJ, Radomski MW, Dawson KA, et al. (2013) Nanoparticle adhesion to the cell membrane and its effect on nanoparticle uptake efficiency. J Am Chem Soc 135: 1438-1444.
13. Miyake N, Sato T, Maki Y (2013) Effect of zeta potentials on bovine serum albumin adsorption to hydroxyapatite surfaces. Bull Tokyo Dent Coll 54: 97-101.
14. Jachimska B, Pajor A (2012) Physico-chemical characterization of bovine serum albumin in solution and as deposited on surfaces. Bioelectrochemistry 87: 138-146.
15. Horie M, Fujita K, Kato H, Endoh S, Nishio K, et al. (2012) Association of the physical and chemical properties and the cytotoxicity of metal oxide nanoparticles: metal ion release, adsorption ability and specific surface area. Metallomics 4: 350-360.
16. Horie M, Nishio K, Kato H, Shinohara N, Nakamura A, et al. (2010) *In vitro* evaluation of cellular responses induced by stable fullerene C60 medium dispersion. J Biochem 148: 289-298.
17. Xia T, Zhao Y, Sager T, George S, Pokhrel S, et al. (2011) Decreased dissolution of ZnO by iron doping yields nanoparticles with reduced toxicity in the rodent lung and zebrafish embryos. ACS Nano 5: 1223-1235.
18. Patil S, Sandberg A, Heckert E, Self W, Seal S (2007) Protein adsorption and cellular uptake of cerium oxide nanoparticles as a function of zeta potential. Biomaterials 28: 4600-4607.
19. Horie M, Nishio K, Endoh S, Kato H, Fujita K, et al. (2013) Chromium(III) oxide nanoparticles induced remarkable oxidative stress and apoptosis on culture cells. Environ Toxicol 28: 61-75.
20. Jiang X, Miclaus T, Wang L, Foldbjerg R, Sutherland DS, et al. (2014) Fast intracellular dissolution and persistent cellular uptake of silver nanoparticles in CHO-K1 cells: implication for cytotoxicity. Nanotoxicology .
21. Sabella S, Carney RP, Brunetti V, Malvindi MA, Al-Juffali N, et al. A General Mechanism for Intracellular Toxicity of Metal-Containing Nanoparticles. Nanoscale. In Press.
22. Palmer LG (1987) Ion selectivity of epithelial Na channels. J Membr Biol 96: 97-106.
23. Jones KT, Sharpe GR (1994) Ni<sup>2+</sup> blocks the Ca<sup>2+</sup> influx in human keratinocytes following a rise in extracellular Ca<sup>2+</sup>. Exp Cell Res 212: 409-413.
24. Cronholm P, Karlsson HL, Hedberg J, Lowe TA, Winnberg L, et al. (2013) Intracellular uptake and toxicity of Ag and CuO nanoparticles: a comparison between nanoparticles and their corresponding metal ions. Small 9: 970-982.
25. Xia T, Kovochich M, Liong M, Madler L, Gilbert B, et al. (2008) Comparison of the mechanism of toxicity of zinc oxide and cerium oxide nanoparticles based on dissolution and oxidative stress properties. ACS Nano 2: 2121-2134.
26. Chen SF, Zhang H, Lin QY (2013) Effect of different water conditions on dissolution of nanosilver. Water Sci Technol 68: 1745-1750.
27. Liu X, Hurt RH, Kane AB (2010) Biodurability of Single-Walled Carbon Nanotubes Depends on Surface Functionalization. Carbon N Y 48: 1961-1969.
28. Karlsson HL, Cronholm P, Gustafsson J, Moller L (2008) Copper oxide nanoparticles are highly toxic: a comparison between metal oxide nanoparticles and carbon nanotubes. Chem Res Toxicol 21: 1726-1732.
29. Moschini E, Gualtieri M, Colombo M, Fascio U, Camatini M, et al. (2013) The modality of cell-particle interactions drives the toxicity of nanosized CuO and TiO<sub>2</sub>, in human alveolar epithelial cells. Toxicol Lett 222: 102-116.
30. Horie M, Nishio K, Kato H, Endoh S, Fujita K, et al. (2014) Evaluation of cellular influences caused by calcium carbonate nanoparticles. Chem Biol Interact 210: 64-76.
31. Horie M, Fukui H, Endoh S, Maru J, Miyauchi A, et al. (2012) Comparison of acute oxidative stress on rat lung induced by nano and fine-scale, soluble and insoluble metal oxide particles: NiO and TiO<sub>2</sub>. Inhal Toxicol 24: 391-400.
32. Horie M (2014) Validity of evaluation of the cellular influence of nanomaterials, Chapter 16, Nanotechnology Vol. 11: Biomaterials, Ed. Navani NK, Sinha S, Ex.Ed. Govil JN, Studium Press LLC. 369-380.
33. Teeguarden JG, Hinderliter PM, Orr G, Thrall BD, Pounds JG (2007) Particokinetics *in vitro*: dosimetry considerations for *in vitro* nanoparticle toxicity assessments. Toxicol Sci 95: 300-312.
34. Kato H, Fujita K, Horie M, Suzuki M, Nakamura A, et al. (2010) Dispersion characteristics of various metal oxide secondary nanoparticles in culture medium for *in vitro* toxicology assessment. Toxicol In vitro 24: 1009-1018.
35. Horie M, Nishio K, Fujita K, Kato H, Endoh S, et al. (2010) Cellular responses by stable and uniform ultrafine titanium dioxide particles in culture-medium dispersions when secondary particle size was 100 nm or less. Toxicol In vitro 24: 1629-1638.
36. Smulders S, Kaiser JP, Zuin S, Van Landuyt KL, Golanski L, et al. (2012) Contamination of nanoparticles by endotoxin: evaluation of different test methods. Part Fibre Toxicol 9: 41.
37. Mahmoudi M, Saeedi-Eslami SN, Shokrgozar MA, Azadmanesh K, Hassanlou M, et al. (2012) Cell "vision": complementary factor of protein corona in nanotoxicology. Nanoscale 4: 5461-5468.
38. Laurent S, Burtea C, Thirifays C, Hafeli UO, Mahmoudi M (2012) Crucial ignored parameters on nanotoxicology: the importance of toxicity assay modifications and "cell vision". PLoS One 7: e29997.
39. ISO/TS 27687:2008 Nanotechnologies – Terminology and definitions for nano-objects – Nanoparticle, nanofibre and nanoplate
40. Grebler S, Gazsó A (2013) Definition des Begriffs "Nanomaterial". Nanotrust dossiers No. 039.
41. Horie M, Komaba LK, Kato H, Nakamura A, Yamamoto K, et al. (2012) Evaluation of cellular influences induced by stable nanodiamond dispersion; the cellular influences of nanodiamond are small. Diam Relat Mater 24: 15-24.